www.tujns.org

Assessment of the lead, cadmium, mercury, and arsenic adsorption capacities of EDTA-modified and umodified cellulose fibres from elephant grass (*Pennisetum purpureum*)

Enugu State University of Science and Technology, Faculty of Applied Natural Sciences, Department of Applied Biochemistry, Enugu State, Nigeria

Cite this article as: Ujah, I. I., Ani, O. N., & Nneji E. O. (2025). Assessment of the lead, cadmium, mercury, and arsenic adsorption capacities of EDTA-modified and umodified cellulose fibres from elephant grass (*Pennisetum purpureum*). *Trakya University Journal of Natural Sciences*, 26(2), 174–181. https://doi.org/10.23902/trkjnat.554289774

Abstract

Heavy metal pollution of water caused by various anthropogenic activities remains a significant global challenge, threatening the supply of clean water. Conventional water remediation approaches are costly with potential environmental risks. Thus, the development of costeffective and biodegradable remediation methods is imperative. This study assessed the heavy metal adsorption capacities of native and EDTA-modified elephant grass (Pennisetum purpureum) cellulose. Elephant grass was collected from Enugu, Nigeria. The samples were washed and shade-dried. Cellulose was extracted via alkali treatment and bleaching, and then modified with EDTA to enhance its adsorptive properties. Batch adsorption experiments were designed to evaluate the capacities of unmodified and modified cellulose fibers to adsorb heavy metals from aqueous solutions under controlled conditions. The metal ion concentrations before and after adsorption were measured using flame atomic absorption spectrophotometry, and the adsorption capacities were calculated. The unmodified and modified cellulose exhibited the highest affinity for Hg(II) and Cd(II), respectively. Both types effectively removed ~70% of the Hg and Cd ions from solution. These results indicated that the unmodified cellulose was particularly effective for Hg removal, while the modified cellulose excelled in adsorbing Cd. They suggest the potential of these materials for the targeted remediation of specific contaminants and also identify them as cost-effective and biodegradable solutions for remediating heavy metal pollution.

Özet

Ceşitli antropojenik faaliyetler sonucu ağır metallerin neden olduğu su kirliliği, temiz su kaynaklarını tehdit eden önemli bir küresel sorun olmaya devam etmektedir. Geleneksel su arıtma yöntemleri maliyetli olup, potansiyel çevresel dezavantajları da bulunmaktadır. Bu nedenle, uygun maliyetli ve biyolojik olarak parçalanabilir arıtma tekniklerinin geliştirilmesi zorunludur. Bu çalışmada, sudan ağır metallerin uzaklaştırılması için fil otundan (Pennisetum purpureum) elde edilen modifiye edilmemiş ve EDTA ile modifiye edilmiş selülozun adsorpsiyon kapasiteleri değerlendirilmiştir. Fil otu Enugu, Nijerya'dan toplanmıştır. Örnekler yıkanmış ve gölgede kurutulmuştur. Alkali işlem ve ağartma yoluyla selüloz ekstraksiyonu yapılan selüloz, adsorpsiyon özelliklerini gelistirmek için EDTA ile modifiye edilmistir. Modifiye edilmemis ve EDTA ile modifiye edilmiş selüloz liflerinin sulu çözeltilerden ağır metalleri adsorbe etme kapasitelerini değerlendirmek için kontrollü koşullar altında toplu adsorpsiyon deneyleri gerçekleştirilmiştir. Adsorpsiyon öncesi ve sonrası metal iyon konsantrasyonları alev atom absorpsiyon spektrofotometresi kullanılarak ölçülmüş ve adsorpsiyon kapasiteleri buna göre hesaplanmıştır. Modifiye edilmemiş ve edilmiş selüloz en yüksek afiniteyi sırasıyla Hg(II) ve Cd(II) için göstermiştir. Her iki selüloz tipi çözeltilerden yaklaşık %70 oranında Hg ve Cd iyonlarını etkili bir şekilde uzaklaştırmıştır. Bulgular, modifiye edilmemiş selülozun Hg gideriminde özellikle etkili olduğunu, modifiye selülozun ise Cd adsorpsiyonunda üstün olduğunu göstermiştir. Bu sonuçlar, her iki tip selülozun belirli kirleticilere karşı hedefli arıtma potansiyeline sahip olduğunu düsündürmektedir. Sonuclar bu maddelerin ağır metal arıtımı için uygun maliyetli ve biyolojik olarak parçalanabilir çözümler olarak ele alınabileceklerine işaret etmektedir.

Keywords: cellulose, heavy metals, biodegradable, remediation, adsorption

Edited by: Bülent Yorulmaz

*Corresponding Author: Innocent Izuchukwu Ujah, E-mail: innocent.ujah@esut.edu.ng

ORCID iDs of the authors: IIU. 0000-0003-4461-4031, ONA. 0000-0001-6533-0869, EON. 0009-0004-4334-8493



Received: 28 March 2025, Accepted: 11 August 2025, Online First: 16 September 2025, Published: 15 October 2025





Introduction

Groundwater, a crucial natural resource supporting human health and socio-economic development, as well as ecosystems, has recently faced escalating contamination issues. The global reliance on groundwater for drinking needs has grown significantly, with ~2.5 billion people depending solely on this resource (Grönwall et al., 2020). Water, as an indispensable element for sustaining life on Earth, plays a pivotal role in socio-economic growth and sustainable development (Okudo et al., 2023). The impacts of water resource mismanagement are further compounded by a range of human activities, posing a severe threat to water quality worldwide (Ighalo & Adeniyi, 2020; Akhtar et al., 2021).

The contamination of water resources by heavy metals, originating from natural sources and human activities, has emerged as a global concern of prominence (Egbueri et al., 2020). Heavy metal pollution of water is a significant environmental issue due to its potential ecological and human health-associated repercussions. Heavy metals, characterized by high atomic weights and densities, can cause toxicity even at low concentrations due to their environmental persistence and cumulative nature (Kumar et al., 2021). These metals, including lead (Pb), mercury (Hg), cadmium (Cd), chromium (Cr), arsenic (As), and nickel (Ni), common in industrial effluents, can disrupt aquatic ecosystems and bioaccumulate in the food chain, thereby threatening aquatic organisms and humans (Ali et al., 2020; Abd Elnabi et al., 2023; Pugazhendhi, 2024).

The water bodies are contaminated by heavy metals from diverse sources, including industrial discharge, agricultural runoff, and geological processes (Aziz et al., 2023). They exert detrimental effects on environmental stability and human well-being, potentially leading to physical, muscular, and neurological disorders (Saha et al., 2019; Ali et al., 2020). Consequently, an indepth understanding of the quality and evolution of groundwater, as well as the associated drivers, is imperative for ensuring long-term water sustainability (Obasi et al., 2020).

The remediation of polluted water involves a process that aims to restore water quality by removing or neutralizing undesirable elements (Hashim et al., 2011). Various techniques and strategies with a focus on mitigating the adverse environmental and health issues stemming from water pollution have been employed (Asefon, 2025). These methods comprise a spectrum of approaches, encompassing physical, chemical, and biological treatments, as well as engineered technologies, all applied together to enhance the safety and quality of water (Trifirò & Zanirato, 2024). Heavy metals, a prominent type of wastewaterderived contaminants, can be effectively eliminated through established techniques such as adsorption, nanofiltration, reverse osmosis, solvent extraction, chemical precipitation, flotation, coagulation, flocculation, membrane filtration, and ion exchange (Gupta et al., 2015). These encompass renewable and non-renewable sources, are adaptable, and utilize a range of chemicals, synthetic and biomaterials, as well as their modified forms (Biswal & Balasubramanian, 2023). Conventional water remediation methods often pose high costs and potential environmental drawbacks (Elbasiouny et al., 2021). Chemical water treatment, though effective, may lead to hazardous leaching (Srivastava, 2021). Especially, biomaterials exhibit considerable potential applicability across various domains, including energy generation, material production, and waste treatment (Chowdhury et al., 2025). In particular, they hold promise for use in environmentally friendly wastewater treatment methods, like adsorption. Agricultural by-products and plant biomass, either modified or not, have demonstrated significant efficacy when harnessed for adsorption. Emerging biosorbents hold potential for metal recovery, cost-effectivity, and minimal secondary waste generation (Bilal et al., 2021). Various materials of crop origin, such as hemicelluloses, cellulose (modified or unmodified), pectin, lignin, and proteins, possess adsorption capabilities, particularly cellulose (Fomina et al., 2014). While certain operational challenges arise with these materials, their modification can overcome such limitations, increasing their adsorption capacity and mitigating issues such as color leaching (Aziz et al., 2024). Therefore, the demand for non-toxic, degradable, cost-efficient, and highly efficient biomaterials has grown, positioning cellulose as a superior alternative (Oyewo et al., 2020). Cellulose, a biodegradable and non-toxic polysaccharide prevalent in various natural resources and agricultural residues, demonstrates applicability in varied water treatment techniques, particularly in removing toxic metals and dyes (Rehman et al., 2020).

Elephant grass (*Pennisetum purpureum*) is a rapidly growing and high-biomass source of cellulose (Yuan et al., 2024). This study investigated the adsorption capacity of unmodified and EDTA-modified cellulose from elephant grass for different concentrations of lead (Pb), cadmium (Cd), arsenic (As), and mercury (Hg) under constant temperature and pH. The objectives were (i) to extract cellulose from elephant grass and chemically modify it with EDTA to improve its heavy metal adsorption capacity; (ii) to investigate and quantify the adsorption capacities of both unmodified and modified cellulose for Pb, Cd, As, and Hg, using batch experiments; (iii) to compare the metal adsorption efficiencies of the unmodified and modified cellulose samples and determine if EDTA modification yields statistically significant improvements in absortion capacity; (iv) evaluate the degree of heavy metal extraction achieved by both forms of cellulose; and (v) assess the overall effect of EDTA modification on their metal-binding performance.

Materials and Methods

Collection of Grass Samples

The elephant grass used was obtained from the Lomalinda Estate, Enugu, Nigeria, where it grows widely during the dry season. The samples were collected by cutting the stems near the base with scissors (Lailaty et al., 2024). Their identity was confirmed by Prof. C. S. Eze of the Department of Applied Biology, Enugu State University, Nigeria. The samples were washed repeatedly with water to remove the extraneous impurities. Subsequently,

they were shade-dried to reduce the moisture content, a step that is crucial for preserving cellulose fiber quality (Kaur et al., 2018).

Cellulose Extraction

The dried elephant grass samples were ground; 114 g of each was soaked in 5% NaOH and mechanically stirred for 2 h at 70°C. Then, the suspension was filtered, and the solid fraction was rinsed with water until a neutral pH was achieved. It was then dried at 100° C for 12 h and bleached by manual stirring with 30% H₂O₂ for 1 h at 90° C. The solid obtained after bleaching was rinsed and dried for 12 h at 100° C (de Morais Teixeira et al., 2011).

EDTA Modification

The cellulose fibres were divided into two portions, and one was EDTA-modified (Igwe et al., 2005). For this, 17 g of the fibres was refluxed in a mixture of 300 mL pyridine and 56.7 g EDTA for 3 h at 70°C. The mixture was cooled, diluted with 300 mL of deionized water, and filtered. The filtered and EDTA-modified fibres were washed copiously with deionized water and dried at 50°C for 12 h. The dried and modified adsorbent was then analyzed. The other portion was left unmodified and also analyzed.

Batch Adsorption Experiments

Equilibrium sorption of selected metal ions onto the cellulose fibres was assessed using 100 mL of each metal ion solution with concentrations varying from 200–1000 mg/L. A constant metal ion–substrate contact period of 1 h, at 29°C, and a pH of 6.7 was applied. Then, 0.2 g samples of the cellulose fiber were added to 20 mL of each solution with a specific concentration of metal ions. The setup was arranged in a rotary shaker at a moderate speed to equilibrate the mixture. After the allotted time, the mixture was rapidly filtered. The metal ion concentration of the filtrate was determined with a flame atomic absorption spectrophotometer. The difference between the initial and final ion concentrations of the solutions was considered the quantity of metal ions adsorbed by the fibres, both unmodified and modified ones.

The heavy metal adsorption capacity of cellulose was determined using Equation 1.

Adsorption Capacity (q) =
$$\frac{(C_0 - C_f) \times V}{m}$$
 (Equation 1)

Where: C_0 = Initial concentration of metal ions in solution before adsorption, C_f = Final concentration of metal ions in solution after adsorption, V = Volume of the metal ion solution, and m = Mass of the cellulose used. The adsorption capacity is typically expressed in mg/g or μ g/g, indicating the amount of metal ions adsorbed per unit mass of cellulose.

Fraction of amount adsorbed =
$$\frac{C_t}{C_0}$$
 (Equation 2)

Where, C_t is the amount of metal ions adsorbed at any time "t;" $C_t = C_0 - C_f$.

The degree of extraction " α " was determined as follows (Nikiforova et al., 2023).

$$\alpha = \frac{C_0 - C_f}{C_0} \times 100\%$$
 (Equation 3)

Statistical Analysis

The statistical significance of the findings was comprehensively assessed using Excel 2016 (Microsoft, WA, USA) and Matplotlib 3.7.0 (https://matplotlib.org/3.7.0/) on Jupyter Notebook 6.5.4 (https://jupyter-notebook.readthedocs.io/en/v6.5.4/). Mean and standard deviations were computed as descriptive statistics for all the measured parameters.

Method Validation

A standard was spiked, run as a sample, and the resulting concentration was determined. The % recovery was then calculated, with values > 90% confirming equipment accuracy, thereby validating the results obtained (Table 1).

$$\%$$
 recovery = spiked - unspiked \times 10 (Equation 4)

Results

Heavy Metal Adsorption Capacity of the Unmodified and Modified Cellulose

The average adsorption capacity of the unmodified cellulose was highest with Hg, followed by Pb, Cd, and As; that of the modified cellulose was highest with Cd, followed by Hg, Pb, and As (Table 2).

Table 1. % recovery calculated using calibration.

Table 10 % lood fell all all all all all all all all all									
Samples	As (ppm)		Hg (ppn	Hg (ppm)		Lead (ppm)		Cd (ppm)	
	1 st	2 nd							
Spike sample (ppm)	9.09	9.08	9.07	9.07	9.28	9.47	10.67	10.72	
Unspike sample (ppm)	0.24	0.29	0.22	0.25	0.298	0.280	0.987	0.955	
Original conc spiked (ppm)	10.00	10.00	10.00	10.00	10.00	10.00	10.00	10.00	
% recovery	88.5	87.9	88.5	88.2	89.82	91.9	96.83	97.65	

Amount injected (standard). All the tested metal ions fell within acceptable recovery limits, indicating that flame atomic absorption spectrophotometer could accurately quantify the heavy metals analyzed.

Table 2. Heavy metal adsorption capacities of the unmodified and	ĺ
modified cellulose.	

Matal	Mean adsorption capacity (mg/g) ± standard deviation					
Metal	Unmodified cellulose	Modified cellulose	<i>p</i> -value			
Pb	42.40 ± 1.31	39.93 ± 16.46	0.754			
Cd	35.50 ± 28.03	46.27 ± 19.16	0.436			
As	19.77 ± 13.98	18.37 ± 7.73	0.828			
Hg	53.63 ± 5.92	44.67 ± 11.14	0.165			

No statistically significant differences were observed in the heavy metal adsorption capacities of the modified and unmodified cellulose. However, modification may still benefit other properties, such as improving physical stability or increasing the adsorption capacity for non-heavy metals. Though the mean adsorption capacity for Pb slightly decreased with modification, the large standard deviation in the capacities between the modified and unmodified samples suggests high variability in Pb uptake between the two. EDTA modification resulted in a higher average adsorption capacity for Cd, but a reduction in variability. However, very little difference was observed between the unmodiafied and modified cellulose in terms of As adsorption capacity. The unmodified cellulose performed better than EDTA-modified cellulose with Hg(II), having a greater mean adsorption and lower variability.

Fractions of Heavy Metals Adsorbed by the Unmodified and Modified Cellulose

The unmodified cellulose had the highest fraction of adsorbed Hg at 1000 mg/L, while the modified one had the maximal fraction of adsorbed Cd at 2000 mg/L.

There was no statistically significant difference in metal adsorption ability between the modified and unmodified cellulose for most of the heavy metals and concentrations tested. However, the *p*-value for 1500 mg/L Cd was marginally significant at 0.051, suggesting that modification might influence Cd adsorption at this concentration. EDTA modification did not consistently improve Pb adsorption, unlike Cd, especially at 1500 mg/L. The adsorption of As varied inconsistently with modification. Unmodified cellulose demonstrated better Hg adsorption, especially at lower concentrations.

Fraction of Pb Adsorbed by the Unmodified and Modified Cellulose

Figure 1 suggests that the highest fraction of Pb adsorbed was by the modified cellulose, but not the unmodified one.

Fraction of Cd Adsorbed by the Unmodified and Modified Cellulose

Figure 2 indicates that the greatest fraction of Cd adsorbed was by the modified cellulose rather than the unmodified one.

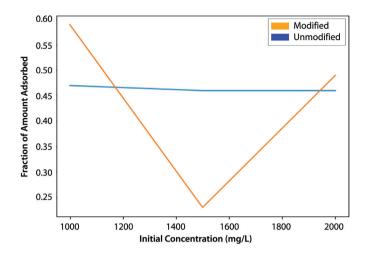


Figure 1. Fraction of Pb adsorbed by the unmodified and modified cellulose.

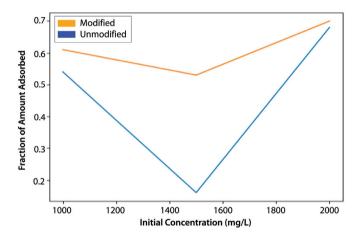


Figure 2. Fraction of the amounts of Cd adsorbed by the unmodified and modified cellulose.

Fraction of As Adsorbed by the Unmodified and Modified Cellulose

Figure 3 suggests that the highest fraction of As adsorbed was by the modified cellulose, but not by the unmodified one.

Fraction of Hg Adsorbed by the Unmodified and Modified Cellulose

Figure 4 shows that the highest fraction of Hg adsorbed was by the unmodified cellulose rather than the modified one.

Degree of Heavy Metal Extraction by the Unmodified and Modified Cellulose

The highest percentage of heavy metals extracted by the unmodified cellulose was with Hg, while that by the modified cellulose was with Cd (Table 4).

Statistically significant variations in heavy metal adsorption capabilities of the modified and unmodified cellulose were observed

for Pb at 1500 mg/L, Cd at 1500 mg/L, and As at 2000 mg/L. These results suggest that cellulose modification may have a metal-type and concentration-dependent effect on the adsorptive ability. At 1500 mg/L, Pb adsorption dropped from 46% (unmodified) to 23 % (modified), with a marked p-value of 0.046. However, at 1000 and 2000 mg/L, the differences were statistically insignificant, indicating no consistent enhancement with modification. At 1500 mg/L, Cd adsorption improved remarkably from 16% to 53% (p = 0.027), but not at 1000 and 2000 mg/L, which may be due to a saturation or equilibrium effect at higher doses. At 2000 mg/L, As adsorption declined significantly from 57% (unmodified) to 3% (modified) (p = 0.043), but increased insignificantly from 9% to 27% at 1500 mg/L. However, a general trend toward improved adsorption was observed, suggesting concentration sensitivity. E.g., unmodified cellulose demonstrated higher Hg adsorption consistently across all concentrations.

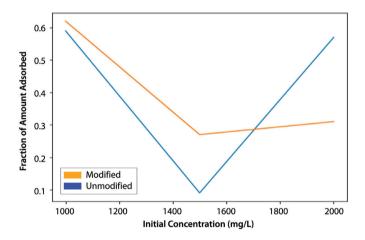


Figure 3. Fraction of As adsorbed by the unmodified and modified cellulose.

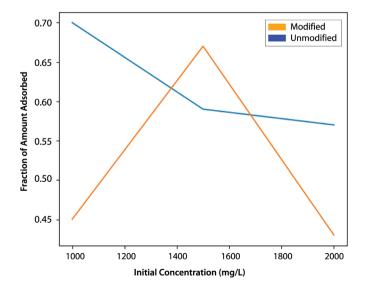


Figure 4. Fraction of Hg adsorbed by the unmodified and modified cellulose.

Table 3. Fractions of heavy metals adsorbed by the unmodified and modified cellulose.

36.4.1	Fraction of adsor	bed amount	<i>p</i> -value	
Metal	Unmodified	Modified		
Pb				
1000 mg/L	0.466	0.589	0.345	
1500 mg/L	0.456	0.229	0.151	
2000 mg/L	0.463	0.491	0.836	
Cd				
1000 mg/L	0.544	0.609	0.636	
1500 mg/L	0.159	0.528	0.051	
2000 mg/L	0.680	0.697	0.851	
As				
1000 mg/L	0.585	0.615	0.834	
1500 mg/L	0.085	0.269	0.272	
2000 mg/L	0.574	0.308	0.144	
Hg				
1000 mg/L	0.702	0.453	0.234	
1500 mg/L	0.593	0.667	0.624	
2000 mg/L	0.572	0.434	0.432	

Table 4. Degree of heavy metal extraction by unmodified and modified cellulose.

Madal	Degree of extra			
Metal	Unmodified	Modified	<i>p</i> -value	
Pb				
1000 mg/L	47	59	0.345	
1500 mg/L	46	23	0.046	
2000 mg/L	46	49	0.836	
Cd			·	
1000 mg/L	54	61	0.636	
1500 mg/L	16	53	0.027	
2000 mg/L	68	70	0.851	
As				
1000 mg/L	59	62	0.834	
1500 mg/L	9	27	0.161	
2000 mg/L	57	31	0.043	
Hg				
1000 mg/L	70	45	0.057	
1500 mg/L	59	67	0.524	
2000 mg/L	57	43	0.176	

Discussion

The mean adsorption capacities indicated that modified cellulose adsorbed Cd the highest, but As the least, across all concentrations. In contrast, unmodified cellulose had the maximum adsorption

capacity for Hg, while the least for As at all concentrations (Table 2). EDTA modification of the cellulose fibers modestly enhanced the Cd adsorption capacity, supporting the role of the chelating groups of cellulose in improving Cd(II) uptake (Fujita et al., 2025). The adsorption of Pb and As was not markedly affected by the modification, suggesting that these metals may interact equally well with both native and functionalized cellulose (Motloung et al., 2023). Conversely, Hg adsorption capacity was greater in the unmodified cellulose, indicating that EDTA modification may introduce functional groups that are less favorable to Hg(II) binding (Riccardi et al., 2013). The adsorption mechanisms of cellulosic materials could explain these patterns. Intrinsic adsorption and columbic interaction are the two primary concepts that may be used to describe the adsorption of metal ions on cellulosic materials (Darmenbayeva et al., 2024). The electrostatic energy of the bonds between the adsorbents and adsorbates produces Coulombic interactions. The interaction intensity mostly depends on the charge of each substrate. The surface areas of the materials dictate intrinsic adsorption. Additionally, surface and microporous adsorptions can be simultaneous (Shi et al., 2022).

The variations in Pb, Cd, As, and Hg ion adsorption are represented as fractions of the adsorbed amount (C_i) vs. the initial concentration (C_o). C_t represents the quantity of metal ions adsorbed at any given time "t." Modified cellulose demonstrated the highest adsorption capacity for Pb, Cd, and As ions, indicating that EDTA modification improved adsorption. The adsorption fractions demonstrate an enhancement in Cd uptake by the EDTAmodified cellulose, particularly at 1500 mg/L Cd, indicating effective chelation (Table 3). Pb and As absorption showed inconsistent responses, with EDTA-functionalization reducing the adsorption efficiency of cellulose with certain concentrations of ions. Hg exhibited a stronger affinity for the unmodified cellulose, suggesting that EDTA ligands may not offer favorable coordination sites for the Hg(II) ions. These findings underscore the importance of matching adsorbent functional groups to the specific chemistry of each metal ion. An enhancement in the adsorption capacity of cellulose post-modification was reported by Kaur et al. (2022), who comprehensively reviewed modified cellulose adsorbents-including EDTA functionalized ones, and their adsorption capacities for Pb, Cd, and Cu. They noted that chemical modifications, like adding EDTA groups, significantly enhanced the adsorption capacity and binding affinity of the unmodified cellulose.

The adsorption abilities revealed a clear metal- and concentration-dependent behavior of cellulose modification (Table 4). EDTA-functionalization significantly improved the removal of Cd at 1500 mg/L, most likely due to robust chelation, while reducing the adsorption of Pb and As at specific concentrations, possibly due to steric effects or changes in surface chemistry. Hg showed a higher affinity for unmodified cellulose, which may be due to the metal-binding limitations of EDTA. These findings signify that certain modifications of adsorbents are suitable for specific contaminants and their expected concentrations. A comparison of Figures 1–4 suggested that modified cellulose had the maximum adsorption

capacity for Cd ions, followed by Hg, As, and Pb. In general, this result indicates that Cd(II) > Hg(II) > As(III) > Pb(II) is the pattern of adsorption onto the modified cellulose. A comparison of the adsorption capabilities of unmodified cellulose for various concentrations of heavy metals indicated a maximum adsorption for Hg(II) at 1000 mg/L. Furthermore, Figures 1–4 demonstrate that unmodified cellulose had the maximum adsorption capacity for Hg ions, followed by those of Cd, As, and Pb. Thus, the general trend of adsorption onto unmodified cellulose is Hg(II) > Cd(II) > As(III) > Pb(II). Gupta et al. (2021) reported a similar trend in their review. In contrast, Kenawy et al. (2018) demonstrated a different trend: Cu(II) > Zn(II) > Cd(II) > Pb > Hg, which was consistent with both the modified and unmodified maize husks.

These findings demonstrate that the type of metal ion, the concentration of the metal ion in solution, and the type of adsorbent modification affect the amounts of metal ions bound by cellulose (Chen et al., 2019). The nature and distribution of the substrate active groups, the type of metal ion-substrate interaction, and size differences in the metal ions can explain the variations in their uptake levels (Wang et al., 2023). The ionic radii were As³⁺: 0.46 Å, Cd²⁺: 0.97 Å, Hg²⁺: 1.02 Å, and Pb²⁺: 1.20 Å. The adsorption rate is inversely proportional to the ionic diameter (Sasan et al., 2023). Similarly, in this study, the ion with the largest radius, Pb(II), had the lowest adsorption. However, the next in size, As(III), went against the trend. This inconsistency can be explained by the surface adsorption of component groups on substrates being more vital for adsorption capacity than microporous adsorption in such cases, which is especially true for Cd(II) and Hg(II) than As(III) ions (Abdelhamid & Mathew, 2021; Aguayo-Villarreal et al., 2024). As a result, compared to As(III), the adsorption of Cd(II) and Hg(II) ions was greater. Statistical analyses unraveled key trends in the adsorption behavior of the unmodified and EDTAmodified cellulose fibers toward heavy metals. While there were no statistically significant differences in the adsorption capacities for Pb, Cd, As, and Hg between the two cellulose types, EDTA modification enhanced Cd adsorption, particularly at its high concentrations. These results suggest that EDTA modification enhances Cd extraction, especially at 1500 mg/L, but may hinder that of Pb and As at certain concentrations. Hg was consistently adsorbed more by unmodified cellulose, indicating unfavorable interactions with the donor O₂ atoms of EDTA.

Conclusion

This study investigated the adsorption capacities of unmodified and EDTA-modified cellulose fibres derived from elephant grass for four toxic heavy metals—Pb, Cd, Hg, and As—from aqueous solutions. The results indicated that both cellulose types possessed considerable potential as biosorbents. However, their affinities varied based on the metal ion involved and the type of chemical modification. The unmodified cellulose demonstrated the highest adsorption capacity for Hg, particularly at its lower concentrations, suggesting a strong inherent affinity for Hg(II) ions. In contrast, EDTA-modified cellulose exhibited significantly improved adsorption for Cd, indicating that EDTA functionalization

increased metal binding, especially for Cd(II). These findings support the hypothesis that EDTA grafting introduces functional groups that facilitate chelation and complexation with specific metal ions. Although the differences in adsorption capacities were not always statistically significant at p < 0.05, modification did enhance the average adsorption and extraction percentages for certain metals—especially Cd at higher concentrations. The adsorption trends observed were Hg(II) > Cd(II) > As(III) > Pb(II) and Cd(II) > Hg(II) > As(III) > Pb(II) for the unmodified and modified cellulose, respectively. The results also suggest that surface adsorption by functional groups may play a more major role than microporous adsorption, particularly for Cd(II) and Hg(II) ions.

In conclusion, both unmodified and modified elephant grass cellulose fibres present biodegradable, cost-effective, and environmentally friendly options for the remediation of heavy metal-contaminated water. In particular, EDTA-modified and unmodified cellulose show promise for the targeted removal of Cd and Hg, respectively.

Ethics

Ethics Committee Approval: Since the article does not contain any studies with human or animal subject, its approval to the ethics committee was not required.

Data Sharing Statement: All data are available within the study.

Footnotes

Author Contributions: Conceptualization: I.I.U., O.N.A., and E.O.N.; Design/methodology: I.I.U., O.N.A., and E.O.N.; Execution/investigation: I.I.U., O.N.A., and E.O.N.; Resources/materials: I.I.U., O.N.A., and E.O.N.; Data acquisition: I.I.U., O.N.A., and E.O.N.; Data analysis/interpretation: I.I.U., O.N.A., and E.O.N.; Writing – original draft: I.I.U., O.N.A., and E.O.N.; Writing – review & editing/critical revision: I.I.U., O.N.A., and E.O.N.

Conflict of Interest: The authors have no conflicts of interest to declare.

Funding: The authors declared that this study has received no financial support.

References

Abd Elnabi, M. K., Elkaliny, N. E., Elyazied, M. M., Azab, S. H., Elkhalifa, S. A., Elmasry, S., Mouhamed, M. S., Shalamesh, E. M., Alhorieny, N. A., Abd Elaty, A. E., Elgendy, I. M., Etman, A. E., Saad, K. E., Tsigkou, K., Ali, S. S., Kornaros, M., & Mahmoud, Y. A.-G. (2023). Toxicity of heavy metals and recent advances in their removal: A review. *Toxics*, 11(7), 580. https://doi.org/10.3390/toxics11070580

Abdelhamid, H. N., & Mathew, A. P. (2021). Cellulose-based materials for water remediation: Adsorption, catalysis, and antifouling. *Frontiers in Chemical Engineering*, *3*, 790314. https://doi.org/10.3389/fceng.2021.790314

Akhtar, N., Syakir Ishak, M. I., Bhawani, S. A., & Umar, K. (2021). Various natural and anthropogenic factors responsible for water quality degradation: A review. *Water*, *13*(19), 2660. https://doi.org/10.3390/w13192660

Ali, M. M., Ali, M. L., Proshad, R., Islam, S., Rahman, Z., Tusher, T. R., Kormoker, T., & Al, M. A. (2020). Heavy metal concentrations in commercially valuable fishes with health hazard inference from Karnaphuli River, Bangladesh. *Human and Ecological Risk Assessment*, 26(10), 2646–2662. https://doi.org/10.1080/10807039.2019.1676635

Asefon, T. (2025). Mitigating water pollution through synergistic chemical and ecological approaches. SSRN Electronic Journal. https://ssrn.com/abstract=5175491

Aziz, K. H. H., Mustafa, F. S., Omer, K. M., Hama, S., Hamarawf, R. F., & Rahman, K. O. (2023). Heavy metal pollution in the aquatic environment: Efficient and low-cost removal approaches to eliminate their toxicity: A review. *RSC Advances*, *13*(26), 17595–17610. https://doi.org/10.1039/D3RA00723E

Bilal, M., Ihsanullah, I., Younas, M., & Shah, M. U. H. (2021). Recent advances in applications of low-cost adsorbents for the removal of heavy metals from water: A critical review. *Separation and Purification Technology*, 278, 119510. https://doi.org/10.1016/j.seppur.2021.119510

Biswal, B. K., & Balasubramanian, R. (2023). Use of biochar as a low-cost adsorbent for removal of heavy metals from water and wastewater: A review. *Journal of Environmental Chemical Engineering*, 11(5), 110986. https://doi.org/10.1016/j.jece.2023.110986

Chen, Q., Zheng, J., Wen, L., Yang, C., & Zhang, L. (2019). A multi-functional-group modified cellulose for enhanced heavy metal cadmium adsorption: Performance and quantum chemical mechanism. *Chemosphere*, 224, 509–518. https://doi.org/10.1016/j.chemosphere.2019.02.138

Chowdhury, M. S., Oliullah, M. S., Islam, R. T., Hurayra, M. A., Al Mahmud, M. Z., & Nazm. (2025). Biomaterials for energy storage: Synthesis, properties, and performance. *Green Technology and Sustainability*, *3*, 100152. https://doi.org/10.1016/j.grets.2024.100152

Darmenbayeva, A., Rajasekharan, R., Massalimova, B., Bektenov, N., Taubayeva, R., Bazarbaeva, K., & Ungarbayeva, A. (2024). Cellulose-based sorbents: A comprehensive review of current advances in water remediation and future prospects. *Molecules*, 29(24), 5969. https://doi.org/10.3390/molecules29245969

de Morais Teixeira, E., Bondancia, T. J., Teodoro, K. B. R., Corrêa, A. C., Marconcini, J. M., & Mattoso, L. H. C. (2011). Sugarcane bagasse whiskers: Extraction and characterizations. *Industrial Crops and Products*, *33*(1), 63–66. https://doi.org/10.1016/j.indcrop.2010.08.009

Egbueri, J. C., & Enyigwe, M. T. (2020). Pollution and ecological risk assessment of potentially toxic elements in natural waters from the Ameka metallogenic district in southeastern Nigeria. *Analytical Letters*, 53(17), 2812–2839. https://doi.org/10.1080/00032719.2020.1759616

Elbasiouny, H., Darwesh, M., Elbeltagy, H., Abo-Alhamd, F. G., Amer, A. A., Elsegaiy, M. A., El-Sheikh, M. A., & Brevik, E. C. (2021). Ecofriendly remediation technologies for wastewater contaminated with heavy metals with special focus on using water hyacinth and black tea wastes: A review. *Environmental Monitoring and Assessment, 193*(7), 449. https://doi.org/10.1007/s10661-021-09236-2

Fomina, M., & Gadd, G. M. (2014). Biosorption: Current perspectives on concept, definition and application. *Bioresource Technology*, *160*, 3–14. https://doi.org/10.1016/j.biortech.2013.12.102

Fujita, S., Sasa, R., Kinoshita, N., Kishimoto, R., & Kono, H. (2025). Nanofibrillated bacterial cellulose nanofiber surface modification with EDTA for the effective removal of heavy metal ions in aqueous solutions. *Materials*, *18*(2), 374. https://doi.org/10.3390/ma18020374

Grönwall, J., & Danert, K. (2020). Regarding groundwater and drinking water access through a human rights lens: Self-supply as a norm. *Water*, 12(2), 419. https://doi.org/10.3390/w12020419

Gupta, A., Sharma, V., Sharma, K., Kumar, V., Choudhary, S., Mankotia, P., Thakur, P., & Mishra, P. K. (2021). A review of adsorbents for heavy metal decontamination: Growing approach to wastewater treatment. *Materials*, *14*(16), 4702. https://doi.org/10.3390/ma14164702

Gupta, V. K., Nayak, A., & Agarwal, S. (2015). Bioadsorbents for remediation of heavy metals: Current status and their future prospects. *Environmental Engineering Research*, 20(1), 1–18. https://doi.org/10.4491/eer.2015.018

Hama Aziz, K. H., Fatah, N. M., & Muhammad, K. T. (2024). Advancements in application of modified biochar as a green and low-cost adsorbent for wastewater

- remediation from organic dyes. *Royal Society Open Science*, 11(5), 232033. https://doi.org/10.1098/rsos.232033
- Hashim, M. A., Mukhopadhyay, S., Sahu, J. N., & Sengupta, B. (2011). Remediation technologies for heavy metal contaminated groundwater. *Journal of Environmental Management*, 92(10), 2355–2388. https://doi.org/10.1016/j.jenvman.2011.06.009
- Ighalo, J. O., & Adeniyi, A. G. (2020). A comprehensive review of water quality monitoring and assessment in Nigeria. *Chemosphere*, 260, 127569. https://doi.org/10.1016/j.chemosphere.2020.127569
- Kaur, A., Setia, H., & Wanchoo, P. R. (2018). Cellulose fiber extracted from Napier grass in PVA composites. *Indian Journal of Chemical Technology*, 25(1), 88–93. http://op.niscpr.res.in/index.php/IJCT/article/viewFile/7440/465464738
- Kaur, J., Sengupta, P., & Mukhopadhyay, S. (2022). Critical review of bioadsorption on modified cellulose and removal of divalent heavy metals (Cd, Pb, and Cu). *Industrial & Engineering Chemistry Research*, 61(5), 1921–1954. https://doi.org/10.1021/acs.iecr.1c04583
- Kenawy, I. M., Hafez, M. A. H., Ismail, M. A., & Hashem, M. A. (2018). Adsorption of Cu(II), Cd(II), Hg(II), Pb(II) and Zn(II) from aqueous single metal solutions by guanyl-modified cellulose. *International Journal of Biological Macromolecules*, 107, 1538–1549. https://doi.org/10.1016/j.ijbiomac.2017.10.017
- Kumar, D., & Khan, E. A. (2021). Remediation and detection techniques for heavy metals in the environment. In *Heavy metals in the environment* (pp. 205–222). Elsevier. https://doi.org/10.1016/B978-0-12-821656-9.00012-2
- Lailaty, I. Q., Astutik, S., & Surya, M. I. (2024). The growth response of Rendeu (*Staurogyne elongata* (Neese) Kuntze) to shoot pruning and its propagation by shoot cutting. *Journal of Tropical Biodiversity and Biotechnology*, *9*(1), 77078. https://doi.org/10.22146/jtbb.77078
- Morales-Herrera, V. A., Quintero-Álvarez, F. G., Mendoza-Castillo, D. I., Reynel-Ávila, H. E., Aguayo-Villarreal, I. A., Landin-Sandoval, V. J., & Bonilla-Petriciolet, A. (2024). Assessment and modeling of mercury adsorption on carbon-based adsorbents prepared from *Jacaranda mimosifolia* and guava biomass via pyrolysis and hydrothermal carbonization. *Water Practice & Technology, 19*(4), 1162–1176. https://doi.org/10.2166/wpt.2024.051
- Motloung, M. T., Magagula, S. I., Kaleni, A., Sikhosana, T. S., Lebelo, K., & Mochane, M. J. (2023). Recent advances on chemically functionalized cellulose-based materials for arsenic removal in wastewater: A review. *Water*, *15*(4), 793. https://doi.org/10.3390/w15040793
- Nikiforova, T., Kozlov, V., Razgovorov, P., Politaeva, N., Velmozhina, K., Shinkevich, P., & Chelysheva, V. (2023). Heavy metal ions (II) sorption by a cellulose-based sorbent containing sulfogroups. *Polymers*, *15*(21), 4212. https://doi.org/10.3390/polym15214212
- Obasi, P. N., & Akudinobi, B. B. (2020). Potential health risk and levels of heavy metals in water resources of lead–zinc mining communities of Abakaliki, southeast Nigeria. *Applied Water Science*, 10(7), 1–23. https://doi.org/10.1007/s13201-020-01233-z

- Okudo, C. C., Ekere, N. R., & Okoye, C. O. (2023). Quality assessment of non-roof harvested rainwater in industrial layouts of Enugu, South East Nigeria. *Applied Water Science*, *13*(5), 116. https://doi.org/10.1007/s13201-023-01916-3
- Oyewo, O. A., Elemike, E. E., Onwudiwe, D. C., & Onyango, M. S. (2020). Metal oxide-cellulose nanocomposites for the removal of toxic metals and dyes from wastewater. *International Journal of Biological Macromolecules*, 164, 2477–2496. https://doi.org/10.1016/j.ijbiomac.2020.08.074
- Rehman, M. U., Taj, M. B., & Carabineiro, S. A. (2023). Biogenic adsorbents for removal of drugs and dyes: A comprehensive review on properties, modification and applications. *Chemosphere*, *338*, 139477. https://doi.org/10.1016/j.chemosphere.2023.139477
- Riccardi, D., Guo, H. B., Parks, J. M., Gu, B., Summers, A. O., Miller, S. M., & Smith, J. C. (2013). Why mercury prefers soft ligands. *The Journal of Physical Chemistry Letters*, 4(14), 2317–2322. https://doi.org/10.1021/jz400885f
- Saha, P., & Paul, B. (2019). Assessment of heavy metal toxicity related with human health risk in the surface water of an industrialized area by a novel technique. *Human and Ecological Risk Assessment*, 25(4), 966–987. https://doi.org/10.1080/10807039.2018.1458595
- Saravanan, P., Saravanan, V., Rajeshkannan, R., Arnica, G., Rajasimman, M., Baskar, G., & Pugazhendhi, A. (2024). Comprehensive review on toxic heavy metals in the aquatic system: Sources, identification, treatment strategies, and health risk assessment. *Environmental Research*, 258, 119440. https://doi.org/10.1016/j.envres.2024.119440
- Sasan Narkesabad, Z., Rafiee, R., & Jalilnejad, E. (2023). Experimental study on evaluation and optimization of heavy metals adsorption on a novel amidoximated silane functionalized *Luffa cylindrica*. *Scientific Reports*, *13*(1), 3670. https://doi.org/10.1038/s41598-023-30634-8
- Shi, R. J., Wang, T., Lang, J. Q., Zhou, N., & Ma, M. G. (2022). Multifunctional cellulose and cellulose-based (nano)composite adsorbents. *Frontiers in Bioengineering and Biotechnology*, 10, 891034. https://doi.org/10.3389/fbioe.2022.891034
- Srivastava, V. (2021). Grand challenges in chemical treatment of hazardous pollutants. *Frontiers in Environmental Chemistry*, 2, 792814. https://doi.org/10.3389/fenvc.2021.792814
- Trifirò, F., & Zanirato, P. (2024). Water purification: Physical, mechanical, chemical and biological treatments. *Mathews Journal of Pharmaceutical Science*, 8, 42. https://doi.org/10.30654/MJPS.10042
- Wang, R., Ren, J., Ren, H., Tao, L., Wu, C., Sun, X., & Lv, M. (2023). Enhanced adsorption of Cu^{2+} from aqueous solution by sludge biochar compounded with attapulgite-modified Fe. *Water*, *15*(23), 4169. https://doi.org/10.3390/w15234169
- Yuan, J., Liu, G., Liu, P., & Huang, R. (2024). Comprehensive assessment of elephant grass (*Pennisetum purpureum*) stalks at different growth stages as raw materials for nanocellulose production. *Tropical Plants*, *3*(1), Article tp-0024-0013. https://doi.org/10.48130/tp-0024-0013